

Anomalous Pressure Dependence of the Superconducting Transition Temperature in FeSe_{1-x} Studied by DC Magnetic Measurements

Kiyotaka MIYOSHI, Yuta TAKAICHI, Eriko MUTOU, Kenji FUJIWARA, and Jun TAKEUCHI

Department of Material Science, Shimane University, Matsue 690-8504

The pressure dependence of superconducting transition temperature T_c has been investigated through the DC magnetic measurements for FeSe_{0.8} and FeSe_{1.0}. For both samples, with increasing pressure P , the T_c - P curve exhibits a two-step increase, showing a local maximum of ~ 11 K at $P \sim 1.0$ GPa and a rapid increase with an extremely large pressure coefficient for $P > 1.5$ GPa. T_c saturates at ~ 25 K (21 K) in FeSe_{1.0} (FeSe_{0.8}) for $P > 3$ GPa. A rapid decrease in superconducting volume fraction is observed with an increase in T_c above 1.5 GPa, suggesting the presence of electronic inhomogeneity.

KEYWORDS: FeSe, high pressure, superconductivity, DC magnetization

Since the discovery of superconductivity in LaFeAsO_{1-x}F_x ($T_c = 26$ K),¹ a great deal of effort has been devoted to explore new superconductors in the related compounds, leading to a rich variety of Fe-based superconductors, such as Ba_{1-x}K_xFe₂As₂,^{2,3} Li_{1-x}FeAs^{4,5} and FeSe,⁶ and an increase in T_c up to 55 K, which is demonstrated by replacing La with Sm in LaFeAsO_{1-x}F_x.⁷ Indeed, the appearance of superconductivity in Fe-based compounds is intriguing because these compounds are mostly magnetic. The superconducting phase is therefore in the vicinity of the magnetic phase suggesting the possible pairing mechanism of the magnetic origin.

The application of pressure also increases T_c in LaFeAsO_{1-x}F_x. The measurements of electrical resistivity (ρ) under pressure have been performed by Takahashi *et al.*, suggesting that T_c increases with increasing pressure P and shows a maximum of 43 K at $P \sim 4$ GPa.^{8,9} In contrast, T_c for NdFeAsO_{1-x}F_x has been found to decrease monotonically from 54 to 16 K by the application of pressure up to 18 GPa.¹⁰ The rapid increase in T_c under pressure in LaFeAsO_{1-x}F_x is expected, considering that SmFeAsO_{1-x}F_x with a higher T_c of 55 K has smaller lattice constants. It is somewhat surprising that the maximum of T_c for LaFeAsO_{1-x}F_x is fairly lower than 55 K. In SrFe₂As₂, pressure-induced superconductivity has been found through the measurements of $\rho(T)$.^{11,12} The application of pressure affects T_c strongly because it gives rise to structural modulations in the compound. It is important to elucidate the relationship between T_c and the local lattice deformation under pressure to gain more insight into the mechanism of superconductivity.

FeSe has a PbO-type crystal structure composed of the stacking layers of Fe₂Se₂, which is analogous to the Fe₂As₂ layers commonly contained in iron-arsenide-based superconductors. The occurrence of superconductivity below $T_c \sim 8$ K has been reported first by Hsu *et al.* for FeSe_{0.88}.⁶ Fang *et al.* have studied the superconductivity of Fe(Se_{1-x}Te_x)_{0.82} and found that Fe(Se_{0.4}Te_{0.6})_{0.82} has a T_c of ~ 14 K.¹³ Moreover, Mizuguchi *et al.* have found that the application of pressure increases the T_c of FeSe in the $\rho(T)$ measurements.¹⁴

They suggest that T_c is 27 K at $P = 1.48$ GPa, regarding the onset temperature of resistivity drop as T_c . Recently, Medvedev *et al.* have performed the $\rho(T)$ measurements under high pressure, suggesting that T_c shows a broad maximum of ~ 37 K at $P \sim 9$ GPa.¹⁵ They also adopt the onset of resistivity drop as T_c . There are some other groups who have reported the T_c - P relation determined from the onset of resistivity drop.^{16,17} In contrast, Masaki *et al.* have defined T_c by zero resistance temperature and suggested that the pressure dependence of T_c shows a plateau between $P = 0.5$ –1.5 GPa and a broad maximum of 21 K at $P \sim 3.5$ GPa in FeSe_{0.92}.¹⁸ It is a difficult problem to determine T_c from the resistivity data when the resistivity drop occurs over a wide temperature range under pressure. The pressure dependence of T_c in FeSe is currently a subject of controversy.

In the present work, we have performed DC magnetization measurements for FeSe_{1-x} ($x = 0$ and 0.2) under pressure using a diamond anvil cell (DAC) to determine the T_c - P relation precisely. Our DC magnetic measurement using DAC is a powerful technique to establish the T_c - P relation, since T_c is uniquely determined from the diamagnetic onset temperature. For AOs₂O₆ (A = K, Rb, Cs) pyrochlore superconductors, the characteristic T_c - P relations have been successfully revealed by the measurements.¹⁹ In this Letter, it has been found that the T_c - P curve is nonmonotonic and shows a maximum at $P \sim 1.0$ GPa and an abrupt increase for $P > 1.5$ GPa followed by the saturation at $T_c \sim 25$ K (21 K) for $P > 3$ GPa in FeSe_{1.0} (FeSe_{0.8}). The T_c - P curves are qualitatively similar to that determined by Masaki *et al.*¹⁸

The polycrystalline samples with nominal compositions FeSe_{1-x} ($x = 0$ and 0.2) used in this study were synthesized by a solid-state reaction technique similar to that described in the literature.^{6,13,14} T_c at ambient pressure determined from the diamagnetic onset was ~ 7 K for both samples. For the magnetic measurements under high pressure, a miniature DAC with an outer diameter of 8 mm was used to generate high pressure and combined with a sample rod of a commercial SQUID magnetometer. The details of the DAC are given elsewhere.²⁰ The FeSe_{1-x} sample was loaded into the gasket

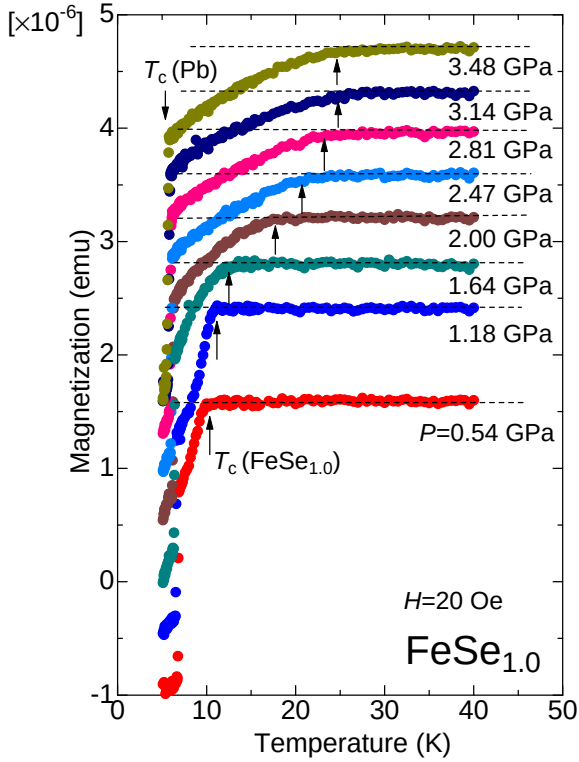


Fig. 1. (Color on line) Temperature dependence of zero-field-cooled DC magnetization for FeSe_{1.0} under various pressures. The data are intentionally shifted along the vertical axis for clarity.

hole together with a small piece of high-purity lead (Pb) to realize the *in situ* observation of pressure by determining the pressure from the T_c shift of Pb. Magnetization data for the small amounts of FeSe_{1-x} and Pb were obtained by subtracting the magnetic contribution of DAC measured in an empty run from the total magnetization data. Most of the measurements have been done by using Daphne oil 7373 as a pressure transmitting medium. Daphne oil 7474 that solidifies at $P_c \sim 3.7$ GPa at room temperature, which is higher than P_c for Daphne 7373 (~ 2.2 GPa), was also used.

We show the temperature variations of zero-field-cooled DC magnetization M measured with a magnetic field of $H = 20$ Oe for FeSe_{1.0} under various pressures in Fig. 1. In the figure, the $M-T$ curve at $P = 0.54$ GPa exhibits a sudden decrease at ~ 10 K, indicating the superconducting transition of FeSe_{1.0}. In addition, a sharp decrease at ~ 7 K that corresponds to the diamagnetic onset of Pb for pressure calibration is observed. A sharp diamagnetic response of FeSe_{1.0} is also observed at $P = 1.18$ GPa, indicating $T_c \sim 11$ K, slightly higher than T_c at $P = 0.54$ GPa. At $P = 1.64$ GPa, T_c is further increased to 12.5 K, but the superconducting transition appears to lose its sharpness. On further application of pressure up to $P = 3.14$ GPa, T_c increases very rapidly and reaches 25 K, although the transition becomes even broader. The $M-T$ curve at $P = 3.48$ GPa also indicates $T_c \sim 25$ K, suggesting that T_c is independent of pressure above $P \sim 3$ GPa.

To clarify the pressure variation in T_c in FeSe_{1.0} in detail, the $M-T$ data under pressure were collected by changing pressure in small steps. The results for $P < 2$ GPa are shown in Fig. 2. In the figure, it is found that T_c at $P = 0.82$ GPa is ~ 11 K, which is higher than T_c at $P = 0.42$ GPa. However, T_c gradually decreases to ~ 10.5 K as pressure increases from 0.82 to 1.42 GPa, suggesting that T_c exhibits a local maximum near $P \sim 0.82$ GPa. Above $P = 1.42$ GPa, a rapid increase in T_c is observed. In the inset of Fig. 2, the $M-T$ curves obtained at higher pressures up to $P = 4.78$ GPa are shown. As seen in the inset, a rapid increase in T_c is also seen above $P = 1.90$ GPa, and the saturation of T_c is marked for $P \geq 2.67$ GPa.

We have also performed $M-T$ measurements at various pressures for FeSe_{0.8} in order to investigate the sample dependence of the T_c-P relation. Figure 3 shows the results of the measurements. In Fig. 3, it is found that the $M-T$ curve at $P = 0.96$ GPa indicates $T_c \sim 11.5$ K, which is the highest T_c for $P \leq 1.61$ GPa. This suggests a local maximum of T_c at $P = 0.8-1$ GPa, similar to the case of FeSe_{1.0}. Furthermore, a rapid increase in T_c is demonstrated in the $M-T$ curves above $P = 1.61$ GPa. The $M-T$ curves above $P = 2.35$ GPa suggest a saturation tendency of T_c . The $M-T$ curves are also shown in the inset of Fig. 3, where T_c is found to take a constant value of ~ 21 K for $P \geq 3.6$ GPa. We should note that the slope of the $M-T$ curve below T_c and the amplitude of magnetization at 5 K decrease significantly with increasing pressure up to 3.54 GPa, indicating a decrease in superconducting volume fraction under high pressure. The behavior appears above $P = 1.61$ GPa, similar to that observed in FeSe_{1.0}. In Fig. 3, the volume fraction $p(\frac{1}{2}T_c)$ at $P = 3.54$ GPa is estimated to be $\sim 1/4$ of that at $P = 0.62$ GPa by comparing the amplitude of magnetization at $T = \frac{1}{2}T_c$. For $P > 2.5$ GPa, the volume fraction appears to be pressure independent.

T_c for FeSe_{1.0} and FeSe_{0.8} is plotted as a function of pressure in Figs. 4(a) and 4(b), respectively. For both samples, it is found that the T_c-P curve exhibits a maximum of ~ 11 K at $P \sim 1.0$ GPa. By the further application of pressure, T_c is found to increase rapidly with an extremely large pressure coefficient of $dT_c/dP \sim 10$ K/GPa after the sharp upturn at $P \sim 1.5$ GPa. Above $P \sim 3$ GPa, T_c for FeSe_{1.0} saturates and takes a constant value of ~ 25 K. In FeSe_{0.8}, T_c is also pressure independent above $P \sim 3$ GPa, reaching 21 K. The T_c-P curve for FeSe_{0.8} is almost identical to that determined from the zero resistive temperature for FeSe_{0.92} by Masaki *et al.*,¹⁸ but these curves are different from those determined from the onset of resistivity drop.¹⁵⁻¹⁷ Thus, the diamagnetic onset agrees with the zero resistive temperature in the FeSe superconductor for a wide pressure range, and they are considered as reliable markers of T_c . It should be noted that T_{cm} , the maximum of T_c for $P > 3.0$ GPa, is ~ 25 K for FeSe_{1.0} but it is ~ 21 K for FeSe_{0.8} and FeSe_{0.92}.¹⁸ T_{cm} appears to depend on the presence of Se deficit. However, the composition x of our specimens is nominal and the exact value is unknown. Recently, McQueen *et al.* have prepared the specimens from iron pieces and selenium shot so as to prevent the formation of spurious oxides and defects, and showed that Fe_{1.01}Se (FeSe_{0.99}) and Fe_{1.02}Se

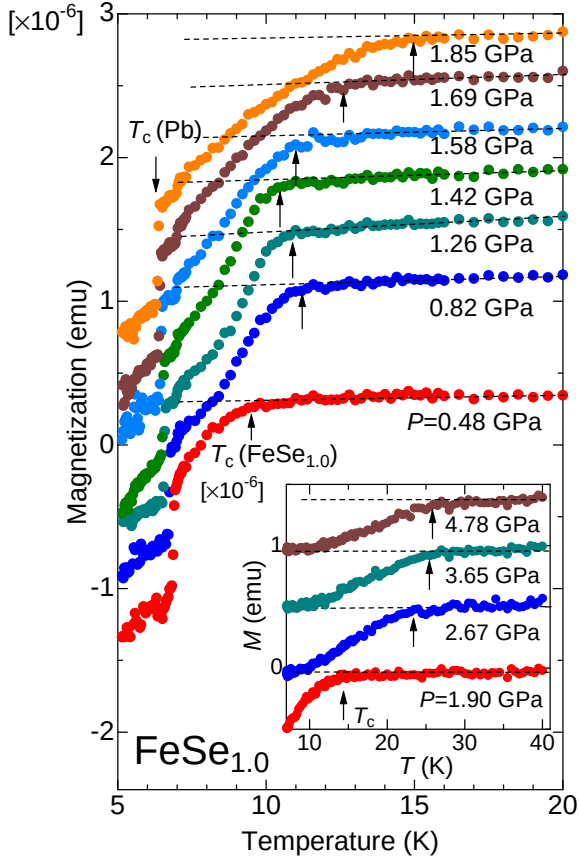


Fig. 2. (Color on line) Zero-field-cooled DC magnetization versus temperature curves for $\text{FeSe}_{1.0}$ at pressures up to 2 GPa. The inset shows those obtained at higher pressure. The data are intentionally shifted along the vertical axis for clarity.

($\text{FeSe}_{0.98}$) are superconducting but $\text{Fe}_{1.03}\text{Se}$ ($\text{FeSe}_{0.97}$) is not, suggesting that the superconductivity of FeSe is destroyed by very small changes in stoichiometry.²¹ They have also revealed that a sample prepared from Fe powder starting with a significant iron excess contains secondary phases of Fe and Fe_3O_4 and the main phase of stoichiometric FeSe. Thus, the $\text{FeSe}_{0.8}$ samples used in this study are considered to contain an almost stoichiometric FeSe phase as well as $\text{FeSe}_{1.0}$. Also, $\text{FeSe}_{0.92}$ used in the $\rho(T)$ measurements would contain an almost stoichiometric FeSe phase. The origin of the difference in T_{cm} is unclear, but we could not exclude the possibility that other specimens of slightly different composition exhibit a T_{cm} more than 25 K.

In the insets of Figs. 4(a) and 4(b), the superconducting volume fraction p at $T = \frac{1}{2}T_c$ normalized to that at low pressure $p_0(\frac{1}{2}T_c)$ is plotted as a function of pressure for $\text{FeSe}_{1.0}$ and $\text{FeSe}_{0.8}$, respectively. For both samples, $p(\frac{1}{2}T_c)/p_0(\frac{1}{2}T_c)$ is found to decrease rapidly above ~ 1.5 GPa and shows a constant value of ~ 0.2 above 2.5–3.0 GPa. This indicates that the volume fraction of superconductivity at $\frac{1}{2}T_c$ is reduced to only 20% of the initial value by the application of pressure. Thus, it is found that the rapid increase in T_c above ~ 1.5 GPa accompanies a significant decrease in superconducting volume fraction in the FeSe superconductor. The decrease in vol-

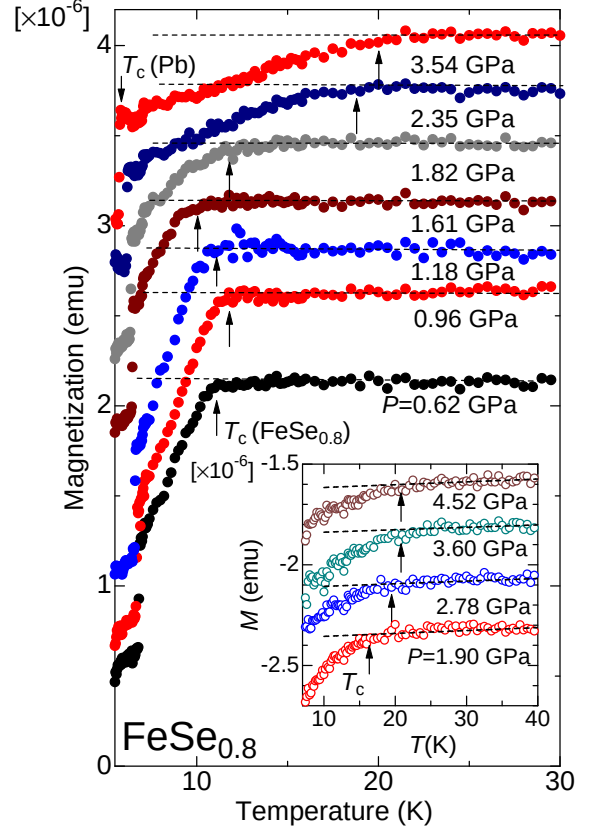


Fig. 3. (Color on line) Zero-field-cooled DC magnetization versus temperature curves for $\text{FeSe}_{0.8}$ at various pressures. The inset shows those obtained in the second run. The data are intentionally shifted along the vertical axis for clarity.

ume fraction above 1.5 GPa was observed regardless of the use of Daphne 7373 or Daphne 7474, indicating that the behavior is not due to the pressure distribution arising from the solidification of Daphne 7373 in the sample space. In addition, our preliminary observation of AC susceptibility (χ) using an indenter-type cell ($P \leq 3$ GPa) also revealed the broadening of the transition and the rapid increase in T_c above 1.5 GPa. Furthermore, the decrease in volume fraction is also inferred from the $\rho(T)$ data above $P = 2$ GPa showing the occurrence of resistivity drop over a wide temperature range.¹⁸ The recent X-ray experiments focused on the pressure evolution of the crystal structure and bonding have revealed that no structural transition is detected below 9 GPa, but a sharp decrease in Se height from the Fe plane is observed.¹⁶ The relationship between the structural modification and the rapid T_c increase above 1.5 GPa has not been clarified. Recently, Imai *et al.* have performed ^{77}Se NMR investigations of FeSe and observed the disappearance of paramagnetic NMR signals below a peak of $1/T_1T$ as a typical signature of a magnetic phase transition or spin freezing.²² The decrease in superconducting volume fraction above 1.5 GPa is considered to be caused by the electronic inhomogeneity realized such as that in the vicinity of the magnetic phase. At the pressures above $P = 3$ GPa, a kink is observed in the $\rho-T$ curve at $T_X \geq 50$ K.¹⁸ The anomaly at T_X may indicate a magnetic phase transi-

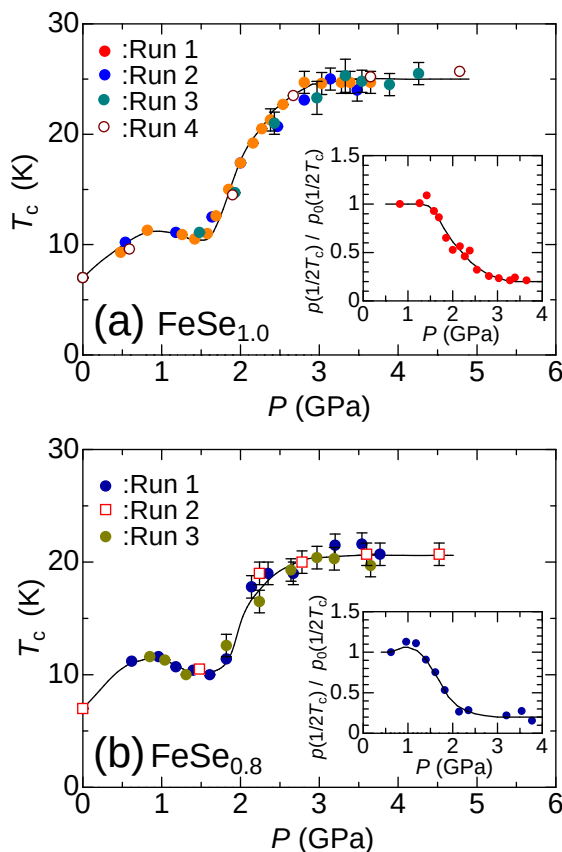


Fig. 4. (Color on line) Pressure (P) dependence of superconducting transition temperature T_c for FeSe_{1.0} (a) and FeSe_{0.8} (b). The inset shows plots of superconducting volume fraction (ρ) at $T = \frac{1}{2}T_c$ normalized to that at low pressure (ρ_0) versus pressure for FeSe_{1.0} (a) and FeSe_{0.8} (b). The solid lines are guides for the eyes.

tion under pressure, although no static magnetic ordering is evidenced from the Mössbauer spectroscopy.¹⁵ In the FeSe superconductor, there is an intriguing possibility that the superconducting phase is divided into two regions in the T – P phase diagram, where an electronically inhomogeneous superconducting state is realized above 1.5 GPa. To elucidate it, further intensive studies are desired above $P=1.5$ GPa.

In summary, it has been found that the T_c – P curve both for FeSe_{1.0} and FeSe_{0.8} exhibits a local maximum of $T_c \sim 11$ K at $P \sim 1$ GPa, then shows an abrupt increase with an extremely large pressure coefficient for $1.5 < P < 3$ GPa, and finally becomes constant for $P > 3$ GPa. The maximum of T_c for $P > 3$ GPa is ~ 25 K (21 K) for FeSe_{1.0} (FeSe_{0.8}). A remarkable feature is the decrease in superconducting volume fraction accompanied by an abrupt increase in T_c above 1.5 GPa. The decrease in volume

fraction is considered as a signature of the electronic inhomogeneity in the superconducting state above 1.5 GPa.

Acknowledgements

This work is financially supported by a Grant-in-Aid for Scientific Research (No. 20540355) from the Japanese Ministry of Education, Culture, Sports, Science and Technology.

- 1) Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono: J. Am. Chem. Soc. **130** (2008) 3296.
- 2) M. Rotter, M. Tegel, and D. Johrendt: Phys. Rev. Lett. **101** (2008) 107006.
- 3) K. Sasmal, B. Lv, B. Lorenz, A. M. Guloy, F. Chen, Y. Y. Xue, and C. W. Chu: Phys. Rev. Lett. **101** (2008) 107007.
- 4) J. H. Tapp, Z. Tang, B. Lv, K. Sasmal, B. Lorenz, P. C. W. Chu, and A. M. Guloy: Phys. Rev. B **78** (2008) 060505(R).
- 5) X. C. Wang, Q. Q. Liu, Y. X. Lv, W. B. Gao, L. X. Yang, R. C. Yu, F. Y. Li, and C. Q. Jin: Solid State Commun. **148** (2008) 538.
- 6) F.-C. Hsu, J.-Y. Luo, K.-W. Yeh, T.-K. Chen, T.-W. Huang, P. M. Wu, Y.-C. Lee, Y.-L. Hung, Y.-Y. Chu, D.-C. Yan, and M.-K. Wu: Proc. Natl. Acad. Sci. U.S.A. **105** (2008) 14262.
- 7) X. H. Chen, T. Wu, G. Wu, R. H. Liu, H. Chen, and D. F. Fang: Nature **453** (2008) 761.
- 8) H. Takahashi, K. Igawa, K. Arii, Y. Kamihara, M. Hirano, and H. Hosono: Nature **453** (2008) 376.
- 9) H. Okada, K. Igawa, H. Takahashi, Y. Kamihara, M. Hirano, H. Hosono, K. Matsubayashi, and Y. Uwatoko: J. Phys. Soc. Jpn. **77** (2008) 113712.
- 10) N. Takeshita, A. Iyo, H. Eisaki, H. Kito, and T. Ito: J. Phys. Soc. Jpn. **77** (2008) 075003.
- 11) H. Kotegawa, H. Sugawara, and H. Tou: J. Phys. Soc. Jpn. **78** (2009) 013709.
- 12) K. Igawa, H. Okada, H. Takahashi, S. Matsuishi, Y. Kamihara, M. Hirano, H. Hosono, K. Matsubayashi, and Y. Uwatoko: J. Phys. Soc. Jpn. **78** (2009) 025001.
- 13) M. H. Fang, H. M. Pham, B. Qian, T. J. Liu, E. K. Vehstedt, Y. Liu, L. Spinu, and Z. Q. Mao: Phys. Rev. B **78** (2008) 224503.
- 14) Y. Mizuguchi, F. Tomioka, S. Tsuda, T. Yamaguchi, and Y. Takano: Appl. Phys. Lett. **93** (2008) 152505.
- 15) S. Medvedev, T. M. McQueen, I. Trojan, T. Palasyuk, M. I. Erements, R. J. Cava, S. Naghavi, F. Casper, V. Ksenofontov, G. Wortmann, and C. Felser: arXiv:0903.2143.
- 16) S. Margadonna, Y. Takabayashi, Y. Ohishi, Y. Mizuguchi, Y. Takano, T. Kagayama, T. Nakagawa, M. Takata, and K. Prasad: arXiv:0903.2204.
- 17) G. Garbarino, A. Sow, P. Lejay, A. Sulpice, P. Toulemonde, W. Crichton, M. Mezouar and M. Nández-Regueiro: Europhys. Lett. **86** (2009) 27001.
- 18) S. Masaki, H. Kotegawa, Y. Hara, H. Tou, K. Murata, Y. Mizuguchi, and Y. Takano: J. Phys. Soc. Jpn. **78** (2009) 063704.
- 19) K. Miyoshi, Y. Takaichi, Y. Takamatsu, M. Miura, and J. Takeuchi: J. Phys. Soc. Jpn. **77** (2008) 043704.
- 20) M. Mito, M. Hitaka, T. Kawae, K. Takeda, T. Kitai, and N. Toyoshima: Jpn. J. Appl. Phys. **40** (2001) 6641.
- 21) T. M. McQueen, Q. Huang, V. Ksenofontov, C. Felser, Q. Xu, H. Zandbergen, Y. S. Hor, J. Allred, A. J. Williams, D. Qu, J. Checkelsky, N. P. Ong, and R. J. Cava: Phys. Rev. B **79** (2009) 014522.
- 22) T. Imai, K. Ahilan, F. L. Ning, T. M. McQueen, and R. J. Cava: Phys. Rev. Lett. **102** (2009) 177005.